

The use of internal friction techniques as a quality control tool in the mild steel industry

L.J. Baker^{a,*}, J.D. Parker^b, S.R. Daniel^c

^a EPSRC Engineering Doctorate Centre in Steel Technology, University of Wales, Corus Group Plc, Swansea, UK

^b University of Wales, Swansea, UK

^c Corus Group Plc, Swansea, UK

Abstract

Advanced sheet steels for automotive body in white applications are continually being developed to provide opportunities for fabricating lighter weight structures which achieve high standards of strength and rigidity. Interstitial free and bake hardenable steels offer significant benefits compared to traditional steel grades. However, to realise the full advantages available, it is vital that target levels of solute carbon and nitrogen levels are achieved through close control of key processing stages. The present paper describes the application of equipment developed to measure internal friction at room temperature and analysis of the interstitial content of selected production steel grades. Progress demonstrates that the accuracy and repeatability of these measurements offers the potential for the data obtained to provide the metallurgical knowledge required to enhance established methods of quality assurance.

© 2003 Elsevier B.V. All rights reserved.

Keywords: Internal friction; Snoek effect; Steel metallurgy

1. Introduction

Increasingly, the steels used in modern automobile production require tight chemistry control. The control of carbon is particularly important since strength and formability can be greatly affected by the presence of this element. Interstitial carbon will drastically reduce the formability of cold rolled and annealed steels and is undesirable in the interstitial free (IF) grades. Conversely, small amounts of interstitial carbon may be of benefit in some steel grades in which an increase in strength can be achieved through the process of strain ageing. These bake hardening (BH) steels are gaining increasing importance in the automotive industry and strong competition between steelmakers to supply this sector requires steel quality to be of the highest standard.

The control of solute carbon is notoriously difficult and tight tolerances are required during steelmaking. For a BH steel to achieve a strength increase of 30–60 MPa, solute carbon must be limited to between 15 and 25 ppm [1]. Deviations from this range will lead to a product which either fails to satisfy the BH criteria or, has excellent BH but fails on room temperature ageing performance. The ability to mea-

sure solute carbon contents quickly and reliably is therefore of considerable benefit to the steelmaker in the development and production of these steel grades.

Traditionally, solute carbon has been measured using internal friction techniques, based on a phenomenon first described by Snoek [2] in 1939 when internal friction (or damping) peaks were produced in an iron sample subjected to an oscillating stress. The interstitial carbon and nitrogen was then removed by annealing in an atmosphere of hydrogen and water vapour and the peaks were eliminated, indicating that the presence of interstitial atoms was responsible for the damping. Snoek's work showed strong damping peaks in steels containing <0.01 wt.% carbon and with advancements in measuring techniques, internal friction has been observed in steels containing <0.001 wt.% carbon, indicating that very small interstitial contents are capable of producing this effect.

The explanation of this effect lies in the atomic behaviour of a crystal of iron containing interstitial carbon or nitrogen. Interstitial atoms occupy octahedral sites in the bcc x-Fe lattice, which can accommodate an atomic radius of 0.019 nm [3]. However, the radii of carbon and nitrogen are 0.08 and 0.07 nm, respectively, producing a distortion in the lattice when these atoms are present in interstitial solution. Each atom is mobile and can make jumps to the nearest neighbour site and, in the absence of any external stress each interstitial

* Corresponding author.

E-mail address: laura.baker@ntlworld.com (L.J. Baker).

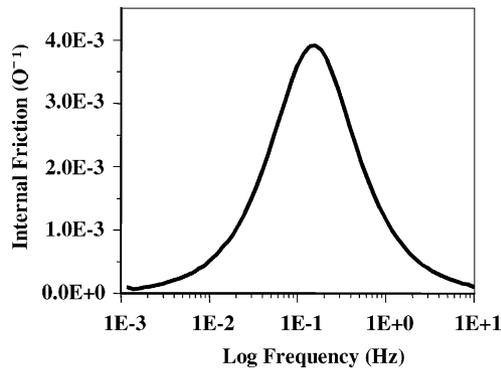


Fig. 1. Typical Snoek peak for interstitial carbon.

site has equal probability of occupation, as the associated lattice distortion is the same. If, however, an external stress is applied in one direction, the corresponding interstice becomes enlarged and acts as a preferential site for interstitial atoms through the reduction in lattice strain. The accumulation of atoms in these interstices will produce a net strain in that direction comprising an elastic and anelastic component. The anelastic strain component will develop over a characteristic time period, τ , which when measured as a function of applied stress frequency or temperature gives rise to the Snoek peak illustrated in Fig. 1. The interstitial carbon peak will typically have a maximum at ~ 0.1 Hz at room temperature allowing it to be easily distinguished from other damping phenomena. The internal friction, Q^{-1} , can be described by the Debye relationship [4]:

$$Q^{-1} = \Delta \frac{\zeta\tau}{1 + (\zeta\tau)^2} \quad (1)$$

where ζ is the radian frequency of the vibration and is equal to $2\zeta f$, where f the frequency of vibration, τ the relaxation time and Δ the relaxation strength. The relaxation strength is proportional to the number of interstitial atoms involved in the stress-induced ordering so that a direct calculation of the interstitial content of the sample can be made. This calculation inevitably involves the use of a proportionality factor, A , of the type in the following equation:

$$Q_{\max}^{-1} = AC^* \quad (2)$$

where Q_{\max}^{-1} is the maximum internal friction (damping) and C^* the interstitial content. To give a value of C^* in wt. ppm, the constant will have dimensions of wt. ppm^{-1} .

The development of modern internal friction equipment has made the measurement of damping relatively simple, however, there is still much debate over the determination of the constant, A , in Eq. (2). This constant may be dependent on metallurgical factors such as crystallographic texture, grain size, dislocation density and concentration of substitutional atoms. It is also highly dependent on the type of equipment used and the temperature of the measurement. It is the aim of the work described here to assess the practical implications of these metallurgical factors on the analysis of

interstitial contents with a view to simplifying the measurement process for use in an industrial context.

2. Experimental

All experimental work was conducted using a Vibran inverted torsion pendulum a schematic of which is shown in Fig. 2. The system, described in detail by Wen et al. [5] operated at room temperature, whilst using sub-resonant frequencies in the range 0.001–10 Hz. The test-piece was positioned in the apparatus by fixing the ends between two vertical rods. The upper rod was suspended by a pulley and counterbalanced by a weight, whilst the lower rod was fixed. An alternating current was applied to the coil, producing a magnetic field which in turn caused a magnet attached to the upper rod to twist, producing a torque in the sample. A laser was transmitted onto a mirror in the upper rod and reflected on to a photocell which detected the movement of the laser and hence the displacement of the sample. Data pairs for torque and displacement were obtained and internal friction was calculated using Fourier transformation. A total of 61 measurements were taken over the frequency range, producing the Snoek peak. Four investigations were made to study the reliability of the equipment and the influence of certain mill processing parameters on the determination of the interstitial content. The composition of the steels used in the investigations are shown in Table 1. With the exception of steel A which was a commercial quality, batch annealed, low carbon steel, the chemistries investigated were all BH grades with expected solute carbon contents of <25 wt. ppm. Steels B and C were batch annealed products, whilst steels D and E were continuously annealed. In these steels, all nitrogen was combined as either aluminium or titanium nitride, so that only solute carbon was analysed. All samples for interstitial analysis were cut to a “dog-bone” geometry with a 4 mm parallel gauge width and 40 mm parallel gauge length using spark erosion cutting techniques to minimise

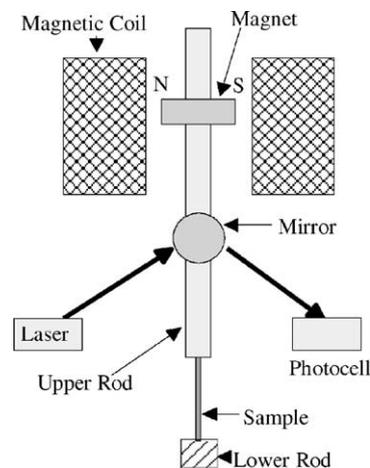


Fig. 2. Schematic diagram of the torsion pendulum.

متن کامل مقاله

دریافت فوری ←

ISIArticles

مرجع مقالات تخصصی ایران

- ✓ امکان دانلود نسخه تمام متن مقالات انگلیسی
- ✓ امکان دانلود نسخه ترجمه شده مقالات
- ✓ پذیرش سفارش ترجمه تخصصی
- ✓ امکان جستجو در آرشیو جامعی از صدها موضوع و هزاران مقاله
- ✓ امکان دانلود رایگان ۲ صفحه اول هر مقاله
- ✓ امکان پرداخت اینترنتی با کلیه کارت های عضو شتاب
- ✓ دانلود فوری مقاله پس از پرداخت آنلاین
- ✓ پشتیبانی کامل خرید با بهره مندی از سیستم هوشمند رهگیری سفارشات